



IJITCE

ISSN 2347- 3657

International Journal of Information Technology & Computer Engineering

www.ijitce.com



Email : ijitce.editor@gmail.com or editor@ijitce.com

Wideband Characterization of Micro strip Technology with Boro float 33 and Some Classic Transparent Glasses

B.SANTHOSH¹, M.SHIVA KUMAR²

Abstract: In this study, we used a broadband characterization approach of microstrip technology based on the S-parameters to determine the technical quality of borofloat 33 glass and other considerably cheaper conventional glasses, coupled with solid metallization. This allowed for the extraction of electromagnetic properties (dielectric permittivity, tangent loss) critical to the development of low-profile antennas. Then, using a vector network analyzer (VNA), the values of nodes S11, S33, S12, and S34 are retrieved. ADS software is used to analyze the measurement data and calculate the loss tangent and dielectric constant. We found $\epsilon_r = 6.5$ and $\tan \delta = 0.0206$ for the classical glass, $\epsilon_r = 6.15$ and $\tan \delta = 0.021$ for the microscope glass, and $\epsilon_r = 4.5$ and $\tan \delta = 0.012$ for the borofloat 33 glass.

Keywords: glass, dielectric permittivity, tangent loss, S parameters, transparent antenna

1. Introduction

The proliferation of wirelessly linked things has resulted in an increase in the frequency with which antennas are encountered. Among the many obstacles that must be overcome, the most significant are the minimization of antennas' aesthetic effect and their incorporation into communication equipment. This is why there is a pressing need for affordable, low-profile, or even completely invisible antennas to be mass-produced. Which will enable the adoption of antennas on glass surfaces (buildings, automobiles, cellphones, etc.) and their placement on historic places and retail centers to not only increase network coverage but also for more discretion to the public owing to their looks. Because of their size, weight, and other physical characteristics, planar antennas may be thought of as separate entities [1]. and they make it possible to use miniaturization strategies. Planar antennas need the use of both dielectric and conductive components in their construction. Glasses and so-called "plastic" materials are the two major groups to look at if dielectric properties are of primary importance.

IoT, or the Internet of Things, is driving the need for novel materials in a wide variety of areas and daily uses (health,

industry of the future, automotive, etc.). These interconnected items may be built on any media, but they all need to be able to exchange data with the outside world. Therefore, we need to be able to create antennas on a wide range of substrates. First, we'll look at materials like borofloat 33, whose guaranteed properties can be verified through this work, and then we'll move on to slightly more "low cost" solutions, whose transparency properties are also guaranteed but for which no estimate has been made of the value of fundamental electromagnetic parameters for the design of antennas, such as the relative permittivity and the loss tangent of the dielectric substrate.

Because it allows for accurate sizing of antennas and, hence, exact prediction of their frequency characteristics prior to manufacture, electromagnetic characterisation of materials has become more significant, if not crucial [2]. Although there are a lot of different ways to measure materials, they may be broken down into two categories: broad-band (transmission lines) and narrow-band (resonant cavity, waveguide, free space).

ASSOCIATE PROFESSOR^{1,2}
ELECTRICAL AND ELECTRONICS ENGINEERING
TRINITY COLLEGE OF ENGINEERING AND TECHNOLOGY, PEDDAPALLY
(bsanthosh.jkd@gmail.com), (shiva.munjam@gmail.com)

The material may be characterized at a single frequency or at a range of discrete frequencies using narrowband techniques that use a cavity resonator. They may be broken down into two categories: - The first is the dielectric resonance method, which uses the dielectric material itself as a resonant element, but is only applicable to low loss samples.

In the second method, known as the perturbation technique, a tiny sample is placed within a resonant cavity to generate a field disturbance, and therefore, a resonant frequency.

range of frequencies of the transmission and reflection coefficients resulting from characteristic changes in impedance and wave speed. The classification of materials is then done by determining the electromagnetic parameters of the substrate under test from these coefficients.

$$\gamma = j$$

2. Presentation of the Technology Used

The electromagnetic characterization method used is broadband measurement method. In this method, only the fundamental waveguide mode (TEM mode in the coaxial lines, quasi-TEM mode in transmission lines and TE₁₀ mode in the waveguides) is assumed to propagate. This technique takes into account the fact that the dielectric substrate will be used in microstrip technology for the design of the antenna, ie with metallization above / below. A measurement using this method involves placing a sample in a section of waveguide line or coaxial line and measuring the diffusion parameters of the two-port complex with a vector network analyzer (VNA) (Figure 1).

The method comprises measuring the reflected (S₁₁ or reflection parameters) and transmitted (S₂₁ or S₁₂) parameters. The relevant parameters are closely related to the complex permittivity and the permeability of the material by equations. For an accurate dielectric measurement, the maximum electric field is required in the sample. Figure 1 illustrates the typical measurement setup with a coaxial cable. This technique is relatively easy to be implemented both in measurement and in the process of extracting parameters.

For TEM mode, the complex relative permeability and permittivity can be found as [6]:

shift [3]. This method may be used with both low- and medium-loss samples.

Attenuation coefficient and phase constant may be calculated from the propagation constant using the relation

Transmission lines are used in wideband techniques, allowing measurements to be taken across a broad frequency range.

$$\gamma = \alpha + j\beta.$$

(1)

For a dielectric material, the propagation coefficient of a wave in a transmission line is related to the complex permittivity of the filler material through the relation [4]:

$$(2) \quad \gamma = \sqrt{\frac{\omega^2 \mu_r \epsilon_r}{c^2} - \left(\frac{2\pi}{\lambda_c}\right)^2}$$

Where ω is the angular frequency, μ_r is the permeability of the material which is equal to 1, c is the speed of light and, λ_c is the cutoff wavelength of the transmission line. In case of a coaxial transmission line supporting TEM propagation the cutoff wavelength is taken to be equal to

infinity. $\epsilon_r = \epsilon' + j\epsilon''$; is the complex permittivity of the material filling the line where, ϵ' is the dielectric constant and ϵ'' is the dielectric loss of the medium. From equation 1 it becomes possible to extract the complex permittivity of the material filling the transmission line.

(2)

S₂₂) and transmitted (S₂₁ or S₁₂) parameters. The relevant

(3)

The advantages of using the transmission / reflectionline include:

- Coaxial lines and waveguides are commonly used to measure samples with medium or high loss;
- They make it possible to more easily determine the permittivity, the permeability and the loss tangent

of the material tested.

However, this broadband measurement technique also presents some constraints:

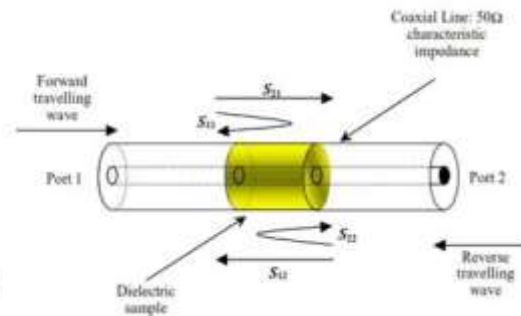
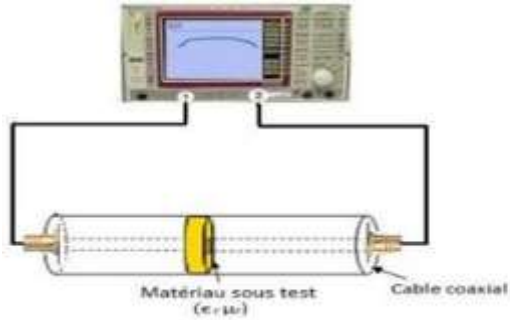


Figure 1. Measurement technique of a dielectric substrate taking into account the application to which it is intended i.e. antenna design [5]

3. Materials and Methods

This broadband microstrip characterization technique was first applied to two conventional glasses (typically microscope glass and classic glass) and whose transparency is around 90% in the visible range, then to borofloat 33 which has 92% transparency (supplier data). The idea is to work with transmission lines of clearly different impedance than 50 Ohms in order to generate sufficiently clear mismatches to be able then to associate a model with the measurement and to identify the values of the parameters ϵ_r and $\tan\delta$ which allow to fit the model to measure. On each glass,

we put two metallizations with copper 35um thick. The upper metallization comprises two lines and the lower metallization constitutes the ground plane. On each line we have two 50 Ohm ports.

One of the 0.4 mm wide lines has an impedance greater than 50 Ohms and the second, 8 mm wide, has an impedance less than 50 Ohms (Figure 2).

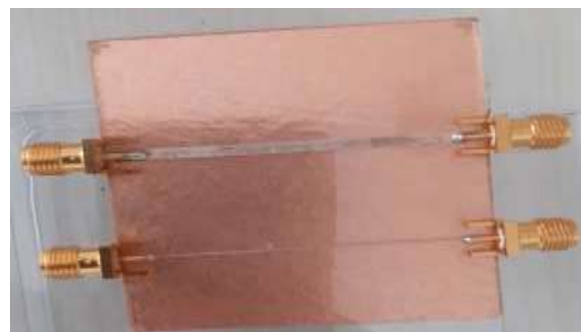


Figure 2. Realization of lines

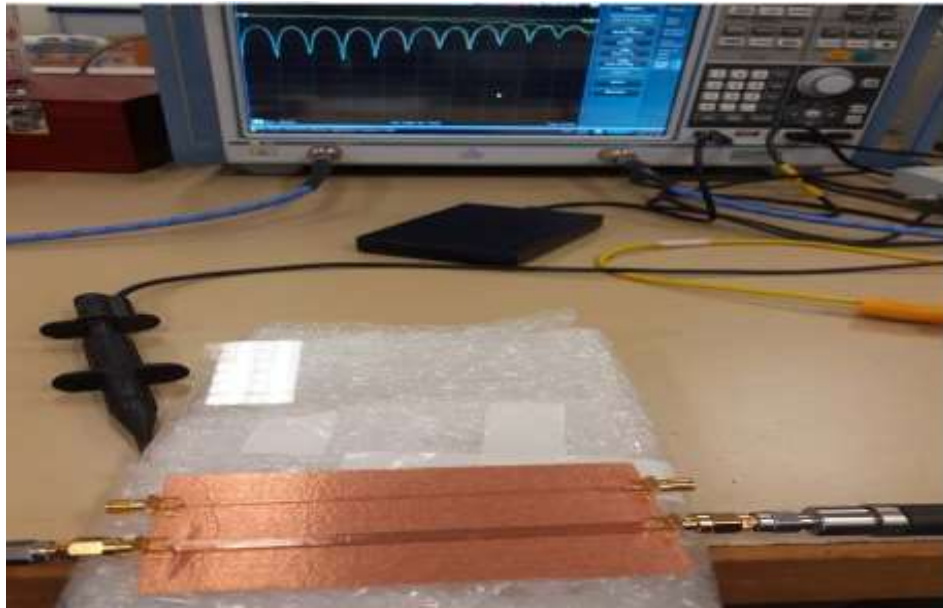


Figure 3. a) measurement configuration on VNA

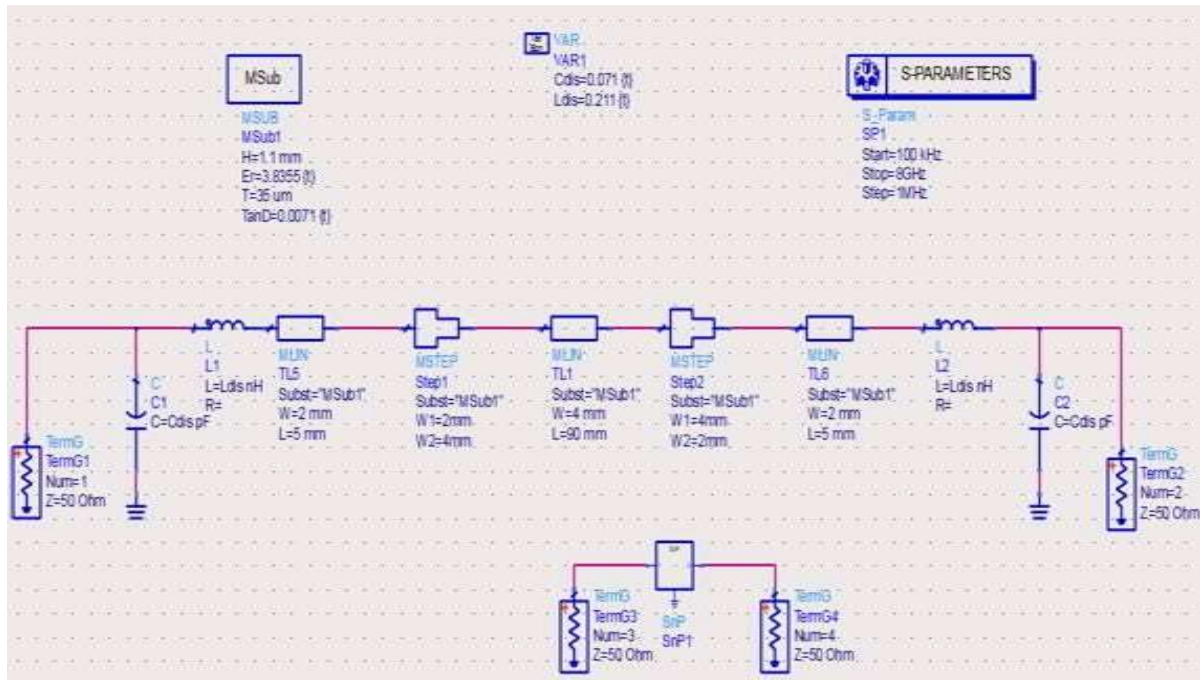


Figure 3.b) Modeling on ADS

After calibrating a network analyzer (VNA), reflection and transmission coefficients or parameters S were measured. Different but common terminations (such an open load, short circuit, or 50 ohm load, for example) need a primary calibration step. Thus, for each line linked to the VNA, we get its realistic values of the parameters S (Figure 3a). The created lines are then simulated in a one-dimensional environment using the ADS (Advanced Design System) program. The form and size of the resulting lines inform the development of the comparable model. Each line has two 50-Ohm ports at its ends, which are represented in Figure 3b by a pair of 50-Ohm generators series-connected to a capacitor C and an inductor L . A 50 Ohm wire is linked to each of the ports. The two ports' 50 Ohm lines are then joined by a third, separate line with the same impedance. To

achieve this agreement between the theoretical (on ADS) and actual (on VNA) response curves, the values of the electromagnetic parameters (r and \tan) and the values (C and L) of the components used in the port models are tweaked. This allows one to calculate the loss tangent and the dielectric constant of the material.

Simulation and measurement Results

Classic Glass

A classic glass is a common and affordable drinking vessel. The results of the measurements used to describe it are shown in Figure 4. The blue lines show experimental findings obtained with the VNA, whereas the red lines indicate ADS modeling results.

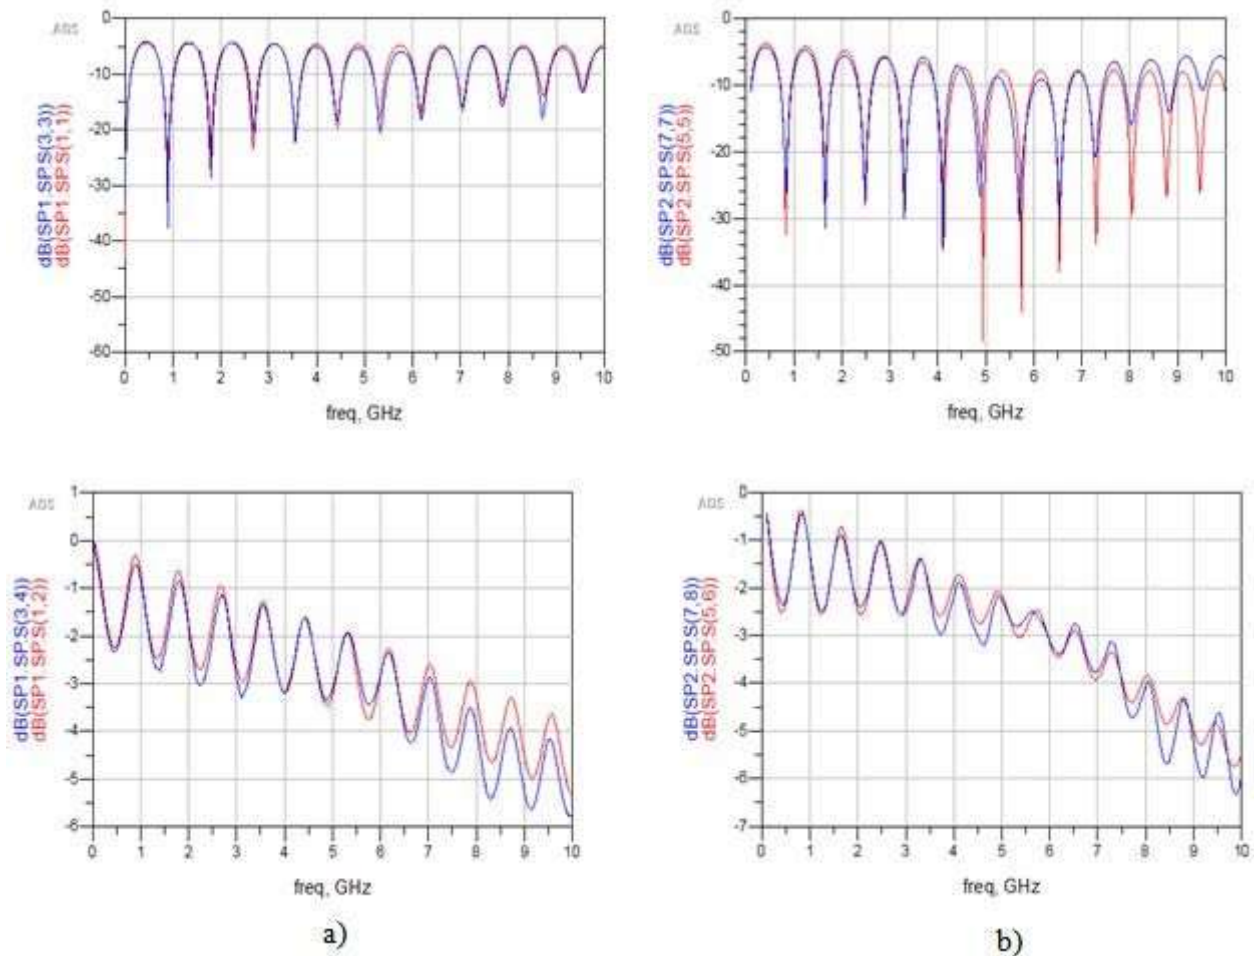


Figure 4. Frequency responses of conventional glass. a) the impedance line $Z < 50$ Ohm (8mm); b) the line of impedance $Z > 50$ Ohm (0.4mm)

Since it may be well correlated with the experiment, the model works well up to 8 GHz. The relative permittivity and loss tangent may be extracted with sufficient accuracy to enable a high-quality antenna design in this frequency range. We measured a loss tangent of 2.06102 and a dielectric permittivity of 6.5. For the antenna's layout, these parameters, especially tan, remain large. Miniaturization is helped by a high dielectric permittivity value, however this reduces the radiation available.

Microscope Glass

As with conventional glass, we made the same measurements with a glass used in microscopy. We obtained a relative dielectric constant $\epsilon_r = 6.15$, which is relatively smaller than that of conventional glass and a loss tangent $\tan\delta = 2.1 \cdot 10^{-2}$. The resonance curves of the S parameters are shown in Figure 5.

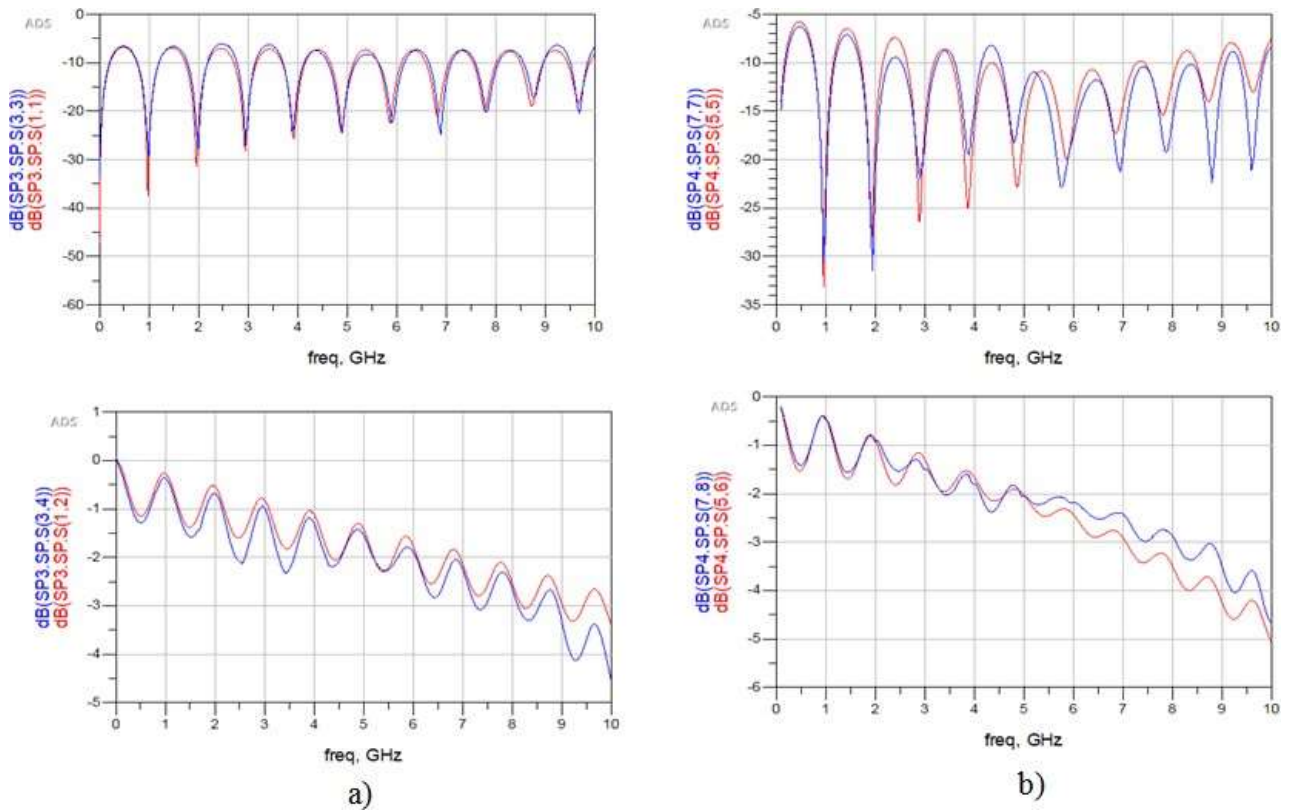


Figure 5. Frequency responses of the microscope glass a) the impedance line $Z < 50 \text{ Ohm}$ (8mm) b) the impedance line $Z > 50 \text{ Ohm}$ (0.4mm)

The electromagnetic parameters of this type of glass are close to those of conventional glass in terms of loss, as are the resonance curves of the S parameters. The microscope glass can therefore be used in the same devices as conventional glass.

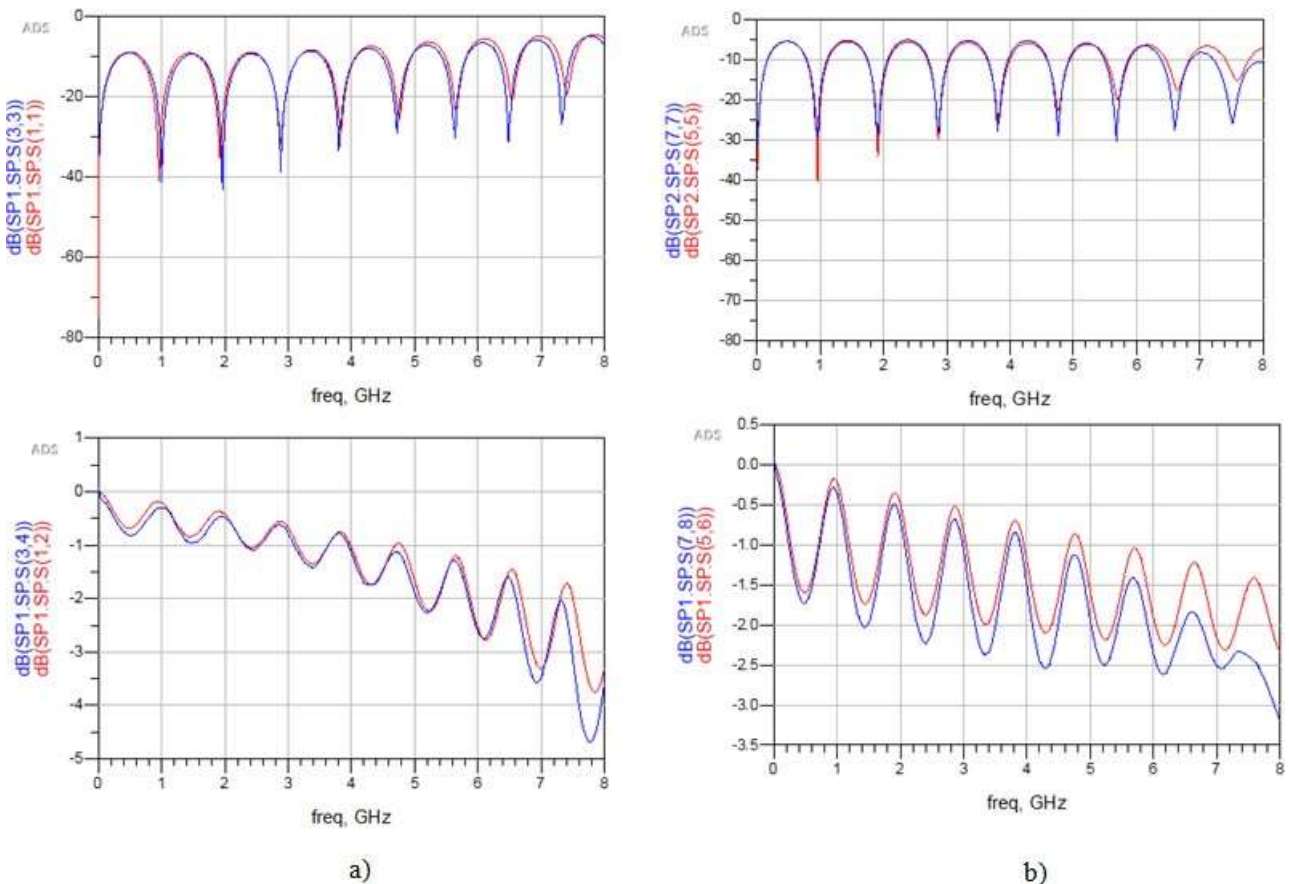


Figure 6. Frequency responses of borofloat 33 glass. a) the impedance line $Z < 50 \text{ Ohm}$ (8mm), b) the impedance line $Z > 50 \text{ Ohm}$ (0.4mm)

Borofloat 33 Glass

By the same method as above, Figure 6 shows us the reflection and transmission coefficient resonance curves of borofloat 33. These resonance curves of the S parameters offer good performance in the 0.1 GHz - 8 GHz band. We obtained $\epsilon_r = 4.5$ as the value of the dielectric permittivity and $\tan\delta = 0.012$ as the value of the loss tangent. Borofloat 33 has a dielectric permittivity and a loss tangent lower than those of the first two glasses (Table 1).

Table 1. Comparison between the values of the electronic parameters of some glasses

| Glasses | Frequency band (GHz) | ϵ_r | $\tan\delta$ |
|--------------------|----------------------|--------------|----------------------|
| Classic glass | 0 à 8 | 6.5 | $2.06 \cdot 10^{-2}$ |
| Microscope glass | 0 à 8 | 6.15 | $2.1 \cdot 10^{-2}$ |
| Borofloat 33 glass | 0 à 8 | 3.9 | $1.2 \cdot 10^{-2}$ |

4. Conclusion

To construct antennas with minimal aesthetic effect and manufacturing expense, we were able to identify their corresponding dielectric characteristics in this article. It first describes the electromagnetic characterisation technique that was used to study the glass substrates in the development of see-through antennas. There are several benefits to using this approach. Broadband in nature, it may be used to determine the loss tangent and relative dielectric permittivity of a dielectric substrate across a range of several gigahertz. Depending on how precise the model is, this extraction may be performed on a very unimportant frequency spectrum. In addition, the configuration/technology that will be used for the design of the antennas is used for the extraction of the substrate's properties. Instead of focusing just on the substrate, as is

the case with certain characterisation methods, this approach characterizes the technology used in the design of the antennas. In contrast, the relative values of permittivity and loss tangent that may be predicted from this sort of material on relatively conventional glasses or on glasses suited for RF applications are shown in this article. With its low dielectric permittivity and appropriate loss tangent, borofloat 33 is the ideal candidate for realizing an antenna with little aesthetic effect and minimal expense.

References

- The authors of this work are [1] Ung Hee Park, Haeng Sook Noh, Seong Ho Son, Kyong Hee Lee, and Soon Ik Jeon. Unique movable ku-band antenna for satellite transmissions. Page numbers for the June 2005 issue of the ETRI Journal are 243-249.
- J.Wang, J.Tao [2] Author: F. Benmohamed; Title: "An Efficient Numerical Method to Analyze Discontinuity of Coaxial Cable" Two-page abstract for the 2017 ACES Symposium on Applied Computational Electromagnetics in Italy.
- 3J. Sheen, "Amendment of cavity perturbation technique for loss tangent measurement at microwave frequencies," Journal of Applied Physics, vol. 102, no. 1, page 014102, July 2007.
- According to [4] M. B. B. Kashif Saeed & Ian C. Hunter Ed, "Planar Microwave Sensors for Characterizing Materials with Complex Permittivity and Their Applications." Technology for Measuring Applications. February 2012 issue of In-Tech, pages 319-350.
- [5] Robert N. Clarke and Andrew P. Gregory. Title: "A Review of RF and Microwave Techniques for Dielectric Measurements on Polar Liquids" August 2006; 5 pages; volume 13, issue 4 of the IEEE Transactions on Dielectrics and Electrical Insulation
- [6] There was a paper titled "Measurement of electromagnetic properties of materials using transmission/reflection method in coaxial line" by J. Shenhui, D. Ding, and J. Quanxing presented at the 2003 Asia Pacific Conference on Environmental Electromagnetics held in China.